



Canadian Geotechnical Journal

Agarose gel as a soil analogue for the development of advanced bio-mediated soil improvement methods

Journal:	<i>Canadian Geotechnical Journal</i>
Manuscript ID	cgj-2019-0496.R2
Manuscript Type:	Article
Date Submitted by the Author:	11-Mar-2020
Complete List of Authors:	Rodriguez Corral, Javier; Newcastle University, Architecture, Planning and Landscape Mitrani, Helen; Newcastle University, Engineering Dade-Robertson, Martyn; Newcastle University, Architecture, Planning and Landscape Zhang, Meng; Northumbria University, Applied Sciences Maiello, Pietro; Northumbria University, Mathematics, Physics and Electrical Engineering
Keyword:	hydrogel, Agarose, soil analogue, soil improvement, bio-mediated
Is the invited manuscript for consideration in a Special Issue? :	Not applicable (regular submission)

SCHOLARONE™
Manuscripts

16 **Abstract**

17 Bio-mediated soil improvement methods (those that use biological processes) have potentially low
18 cost and environmental impact but can be difficult to control to ensure effective results, especially if
19 engineered bacteria are used. A novel application of using agarose gel as a soil analogue is proposed,
20 which can enable development of advanced bio-mediated soil improvement methods by reproducing
21 relevant mechanical properties while allowing complex biological processes to be studied in detail,
22 before testing in soils. It is envisaged that agarose gel will be used instead of soil when developing
23 early-stage prototype methods, as it provides an ideal environment to facilitate growth and
24 monitoring of bacteria. A programme of geotechnical tests and Scanning Electron Microscopy on
25 Agarose Low Melt (LM) gel is presented. The results demonstrate comparable pore size, undrained
26 strength and permeability to soft clays and peats but more linear stress-strain behaviour and higher
27 compressibility. This paper offers proof of this novel concept but further investigation is required as
28 only a single type of agarose, at a single concentration is tested. By varying these factors, along with
29 use of different solvents, there is significant potential to tune the behaviour of the analogue to
30 particular soils or construction scenarios.

31 **Key words**

32 Hydrogel, Agarose, Soil Analogue, Soil Improvement, Bio-mediated, Biological

33

34 Introduction

35 Bio-mediated soil improvement techniques use biological processes to improve soil
36 properties. *Biocementation* can strengthen soils (Whiffen et al. 2007, Ivanov and Chu 2008, Martinez
37 et al. 2014), *biodesaturation* reduces soil saturation through the production of biogas (Chu et al. 2009,
38 DeJong et al. 2013) and *bioremediation* can remove contaminants (White et al. 1998, Stabnikov et al.
39 2015). These techniques have a wide range of applications and potentially low cost (White et al. 1998,
40 Horemans et al. 2017) and environmental impact (DeJong et al. 2009, DeJong et al. 2010).

41 However, despite the potential of bio-mediated methods, there is still significant
42 multidisciplinary research required to optimise and develop these complex processes, to provide more
43 control and certainty of outcome. It is also possible to advance bio-mediated methods further by using
44 Synthetic Biology approaches to engineer biological systems so that their properties and response to
45 external stimulus can be controlled (Endy 2005). Synthetic Biology allows design of living organisms
46 by altering their genetic circuits, enabling them to sense their environment and respond in ways that
47 they would not do naturally. For example, in a previous study the authors have shown how engineered
48 bacteria can be developed to respond to elevated pressure (Dade-Robertson et al. 2018) with the
49 objective of then engineering this bacteria so that it is able to respond to elevated pressure by
50 synthesising material. An application of this would be a responsive bio-mediated ground improvement
51 method which would enable a soil to increase its strength when loaded (Dade-Robertson et al. 2018).

52 Biological systems are complex and sensitive, so a high degree of control over testing
53 conditions is required for the molecular level manipulation of living cells in the early development of
54 a prototype bio-mediated soil improvement method. It is therefore helpful to have a soil analogue
55 which has similar relevant mechanical properties to soils but which allows easier monitoring, greater
56 control of the chemical environment and also minimises risk of contamination from, for example,
57 other microorganisms. Although these will be present in real soils, at the early development stage it
58 is advantageous to minimise complexity. It is proposed that agarose gels can provide such a soil
59 analogue for the early development of advanced bio-mediated soil improvement techniques – a novel

60 concept which has not been previously proposed. This type of gel has a porous structure comparable
61 to cohesive or organic soil, although it is fibrous rather than granular. The gel also allows controlled
62 simulation of a variety of chemical, physical and mechanical properties. These gels are already used
63 routinely in microbiology for culturing and monitoring bacteria so provide ideal conditions for this.

64 Agarose gels have been extensively studied at small scale for a wide range of applications
65 including biomedical applications, tissue engineering, drug delivery, soft electronics and actuators
66 (Zhang and Khademhosseini 2017, Varaprasad et al. 2017, Ionov 2014) but little information exists
67 about their behaviour and properties at a macro-scale relevant to civil engineering. This paper
68 describes a program of geotechnical experimental testing to determine the strength, stress-strain
69 behaviour, permeability, consolidation behaviour and details of the microstructure of Agarose LM gel.
70 It should be noted that Agarose LM gel is not added to soil under any circumstances and the properties
71 reported are for the pure gel only. These properties are then compared to those of cohesive and
72 organic soils, to assess the suitability of agarose for the novel application of a soil analogue for the
73 early development of advanced bio-mediated soil improvement methods.

74 **Materials and methods**

75 **Materials**

76 *Agarose gel*

77 Agarose is extracted from one of several types of marine red algae and is one of the main
78 components of agar. Agarose gels consist of a network of fibres held together by non-covalent
79 hydrogen bonds and microvoids holding water (Stellwagen and Stellwagen 1995). The mechanical
80 properties of the gels are mainly dictated by the fibre-pore structure which depends on several factors
81 including agarose type and concentration (Narayanan et al. 2006). 2-Hydroxyethyl Agarose, or Agarose
82 Low Melt (LM) supplied by Melford Laboratories was used in all experiments.

83 *Solvent*

84 A solution of LB Broth (Miller), provided by Sigma Aldrich (components: 10g/L Tryptone, 10g/L
85 NaCl and 5g/L Yeast Extract), dissolved in distilled water was used where possible to prepare the
86 samples. If the agarose gel is used to develop bio-mediated soil improvement methods as intended, a
87 nutrient broth such as this will be necessary to enable bacteria growth. Therefore, LB broth was
88 chosen as the solvent to give mechanical properties which are as representative as possible for this
89 application. However, for the consolidation tests which were of much longer duration (several weeks),
90 only distilled water was used to avoid the growth of unwanted bacteria in these cases. It is possible
91 that the change in solvent and even growth in bacteria may affect the mechanical properties of the
92 agarose gel however this is outside the scope of the current investigation. Distilled water was also
93 used in the preparation of the samples for Scanning Electron Microscopy, to avoid interference when
94 imaging the structure of the gel.

95 *Kaolinite*

96 The kaolinite used to prepare the clay samples was Kaolin provided by IMERYS Ceramics.

97

98 **Experimental methods**

99 In order to assess Agarose LM gel as an analogue for soil, a range of geotechnical experiments
100 were performed. The experiments were chosen to determine the physical and mechanical properties
101 of the gel of relevance to the behaviour of fine-grained soils. It was anticipated that the behaviour of
102 the agarose gel would be most similar to that of clays due to the pore sizes of these types of soil and
103 the electrostatic forces between clay particles which allow high water adsorption (Knappett and Craig
104 2012).

105 Visualisations of the structure of the gel made with different mass concentrations of agarose
106 and also under load were obtained using Scanning Electron Microscopy (SEM). Analysis of these SEM
107 images allowed estimates of pore size and porosity. The undrained shear strength (c_u) and stress-strain
108 relationship were determined using Unconsolidated Undrained triaxial tests. In triaxial tests, the
109 samples are subjected to a confining pressure or radial stress, σ_3 and an axial stress, σ_1 applied
110 vertically. The permeability of the gels was also investigated using Isotropic Consolidation triaxial tests,
111 where drainage of the pore water at different consolidation pressures is allowed. Permeability is
112 particularly important as it affects the transport and distribution of nutrients and microbes through
113 the porous structure. Finally one-dimensional consolidation of the gels was investigated using an
114 oedometer.

115 *Agarose gel sample preparation*

116 The agarose gel was formed by dissolving Agarose LM powder in distilled water or LB media.
117 This powder has low solubility in these solvents at room temperature, therefore the heterogeneous
118 mixture was heated to 121°C for at least 30 minutes, stirring continuously in order to achieve a
119 homogeneous solution. The solution was then immediately poured into aluminium moulds for triaxial
120 or oedometer testing or 25mm Petri dishes for SEM.

121 For the triaxial tests, 38mm diameter cylindrical moulds were filled with gel to approximately
122 a height-to-diameter ratio of 2. The cylinders were immediately covered with tape in order to avoid
123 evaporation and then stored in a fridge at 4°C for approximately 15 minutes until gelation, with no

124 further curing required. For the oedometer tests, samples were prepared in the same way, although
125 the moulds used in this case were 50mm in diameter and 20mm in height. Samples with mass
126 concentrations of 2%, 4% and 6% m/v (mass/volume) were imaged using SEM and for all geotechnical
127 tests, a concentration of 6% m/v was used. This was chosen after initial investigation determined that
128 this was the highest concentration possible that allowed homogeneous growth of bacteria, which was
129 required for associated studies on developing bacteria-based soil improvement methods.

130 *Kaolinite sample preparation*

131 Kaolin powder was thoroughly mixed with water until a homogeneous mixture was achieved.
132 The mixture was then consolidated at 100kPa for a week. Cylindrical samples were cut from the
133 consolidated clay using 38mm diameter moulds. The top and bottom of the cylinders were then
134 covered with wax in order to avoid changes in the water content and stored in a cool environment
135 until testing.

136 *Saturation of samples*

137 The method of making the agarose gel produces saturated samples. When the powder is
138 mixed with the solvent and heated a dense liquid is formed and some bubbles are present. However
139 during the heating process the solution is mixed continuously and these bubbles can be observed to
140 migrate to the surface and disappear. Once a homogenous solution is achieved, no remaining bubbles
141 are visible and the gels are assumed to be fully saturated. To confirm this is the case, the pore pressure
142 coefficient, B , or Skempton's B-value (Skempton 1954) was obtained before starting all triaxial tests.
143 To determine the B-value, increments of confining stress were applied and the increment in pore
144 pressure measured. It was ensured that the B value was above 0.95, as recommended by British
145 Standard testing methods (British Standards Institution 1990c) and also that the change in pore
146 pressure was instantaneous with the change in confining pressure. B values for the kaolinite samples
147 were also obtained in the same way.

148

149

150 *Scanning Electron Microscope imaging*

151 The scanning electron microscope used was a field emission TESCAN MIRA 3. Agarose gel was
152 prepared as described in 'Agarose gel sample preparation'. Upon gelation, 5mm³ cubes of gel were
153 cut and placed inside 10mL beakers. Liquid nitrogen was then poured into the beakers to guarantee
154 rapid freezing of the samples and avoid structural deformations during the freeze-drying process. The
155 use of ultrafast freezing techniques avoids distortions and deformations of the specimens' structure
156 to as little as the nanometre scale (Robards 1991). The beakers were then placed into a vacuum cell
157 and were freeze-dried under vacuum at -80°C for 24h. Finally, before SEM inspection, the samples
158 were sputter-coated with a layer of platinum between 3nm and 4nm thick using a High Resolution
159 Sputter Coater. The samples were visualised at a very low voltage (1.5kV to 2kV) in order to avoid any
160 damage to the structure.

161 *Triaxial tests*

162 Two different series of triaxial tests were performed using a GDS 50kN digital load frame:
163 Unconsolidated Undrained (UU) tests and Isotropic Consolidation (IC) tests.

164 For the UU triaxial tests, Agarose LM cylinders were produced as described in 'Agarose gel sample
165 preparation' and then demoulded, prepared and tested according to British Standard testing methods
166 (British Standards Institution 1990d). The samples were wrapped in an impervious membrane and
167 confined between impervious end caps before being introduced into the triaxial cell. This allowed
168 maintenance of a constant moisture content. The kaolinite clay samples were also demoulded and
169 tested to failure following the same procedure.

170 For the IC triaxial tests, pressure-volume controllers were attached to the triaxial cell and
171 connected to the top and bottom of the sample, in order to measure and control pore pressures and
172 drainage. Special caps including porous stones were also placed top and bottom of the sample which
173 allowed drainage. The tests were performed according to British Standard testing methods (British
174 Standards Institution 1990c) at different effective stresses (25kPa, 50kPa, 100kPa and 150kPa).

175 *Oedometer tests*

176 50mm diameter disks were prepared as described in ‘Agarose gel sample preparation’ and
177 tested according to British Standard testing methods (British Standards Institution 1990b). Drainage
178 was allowed from both top and bottom of the sample and filter paper was added between the sample
179 and the porous stone to ensure that no gel entered the pores of the stone during the consolidation
180 stage.

181 Agarose gel samples were consolidated anisotropically at different consolidation pressures
182 (3kPa, 6kPa, 12kPa, 25kPa and 50kPa) by applying increments of axial stress. At the end of the
183 consolidation test, the samples were unloaded in the same increments.

184

185 **Results**

186 ***Effect of concentration on microstructure***

187 Fig. 1 shows SEM images of Agarose LM gel samples at different mass concentrations (2%, 4%
188 and 6% m/v), at the same scale, at two different levels of magnification. It can be seen qualitatively
189 that increasing gel concentration results in more densely packed fibres and reduced pore size. The
190 pore diameters shown in each image in the top row of Fig. 1 were measured using ImageJ (an open-
191 source image processing software) and the results are represented in Fig. 2. The reduced pore size at
192 higher concentrations means that it is harder for bacteria to grow homogenously, as they are more
193 constrained. This consideration governed the choice of concentration of hydrogel used for all
194 mechanical tests (see section ‘Agarose gel sample preparation’).

195


196

197


198

199

200 Fig. 1. SEM images of microstructure at mass concentrations of 2% (left), 4% (middle) and 6% (right).
 201 The bottom row is at 10 times the magnification of the top row.

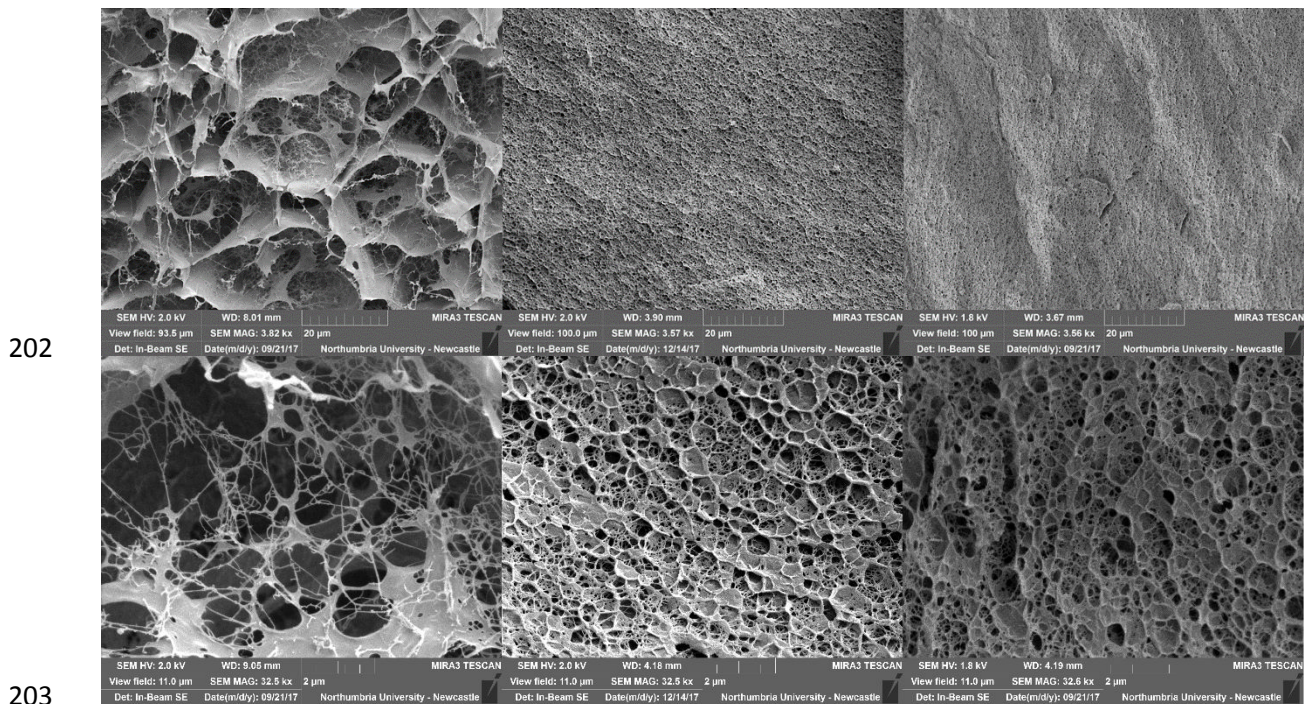

205 Fig. 2. Pore size as a function of agarose concentration.

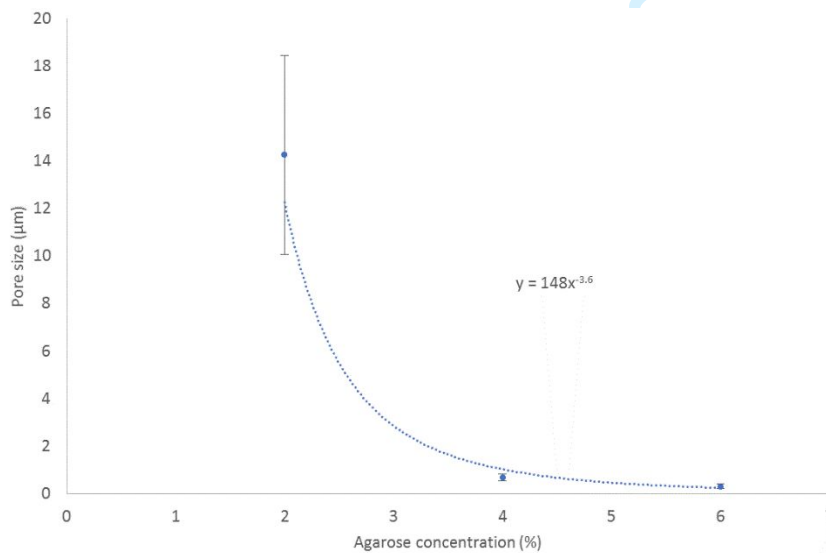

207 The error bars in Fig. 2 show the variation of pore size at each concentration. Due to the
 208 reduced size of the pores, this variation is not so clear for the higher concentrations in Fig. 2 but size
 209 variation is still present, as can be seen qualitatively in the higher magnification images in Fig. 1. The

210 results indicate a relationship between the concentration of agarose C and the pore size, a , of the
 211 form:

$$212 \quad (1) \quad a \sim C^{-\gamma}$$

213 where γ is a constant that depends on the agarose type and the setting temperature (Narayanan et
 214 al. 2006) and is found to be 3.6 in this case. This result differs from those found by previous
 215 researchers, for example Ogston (1958) and de Gennes (1979) who give values of γ between 0.5 and
 216 0.75. This difference may be related to the use of Agarose LM over standard agarose.

217

218 **Porosity, void ratio and moisture content**

219 Ogston et al. (1973) developed a method to determine the volume fraction of fibres ϕ , which
 220 can be calculated as:

$$221 \quad (2) \quad \Phi = \frac{C}{\rho\omega}$$

222 Where C , ρ and ω are concentration of agarose in the gel (m/v), dry agarose density and mass fraction
 223 of agarose in a fibre, respectively. The last two values can be estimated as 1.64 g/mL (Laurent 1967)
 224 and 0.625 (Johnson et al. 1995). From the volume fraction of fibres, ϕ , the porosity n and the void
 225 ratio e can be obtained with the following expressions (Pluen et al. 1999):

$$226 \quad (3) \quad n = 1 - \phi$$

$$227 \quad (4) \quad e = \frac{n}{1-n}$$

228 The moisture content can be also be calculated according to the following expression:

$$229 \quad (5) \quad w = \frac{m_w}{m_{dry}}$$

230 where m_w and m_{dry} are the mass of water and mass of dry solids, respectively.

231 The moisture content was also obtained experimentally for cylinders (50mm in diameter and
 232 20mm in height) of agarose gel, according to British Standard testing methods (British Standards
 233 Institution 1990a). From this, an experimental void ratio can also be obtained with the relationship
 234 between void ratio, moisture content and specific gravity (G_s) for a saturated soil (Smith 2014):

235 (6) $e = wG_s$

236 where w is the water content and G_s is the specific gravity of dry agarose (1.64g/mL as previously).

237 Table 1 represents the theoretical and the experimental values obtained for the porosity, void ratio
 238 and moisture content of 6% m/v Agarose LM gel. The theoretical and experimental values of water
 239 content agree reasonably well and the difference between the values is likely to be due to the
 240 assumptions of dry agarose density and mass fraction of agarose in a fibre, which have not been
 241 measured for this particular Agarose LM gel.


242

243 ***Stress-strain relationship***

244 The stress-strain relationship for samples at different confining pressures is presented in Fig.
 245 3, along with an inset photo showing the failure plane of two Agarose LM samples. From this data the
 246 undrained shear strength, c_u , can be also derived according to British Standard methods (British
 247 Standards Institution 1990d).

248

249 Fig. 3. Stress-strain relationship at different confining pressures, with inset of samples showing
 250 failure surface.

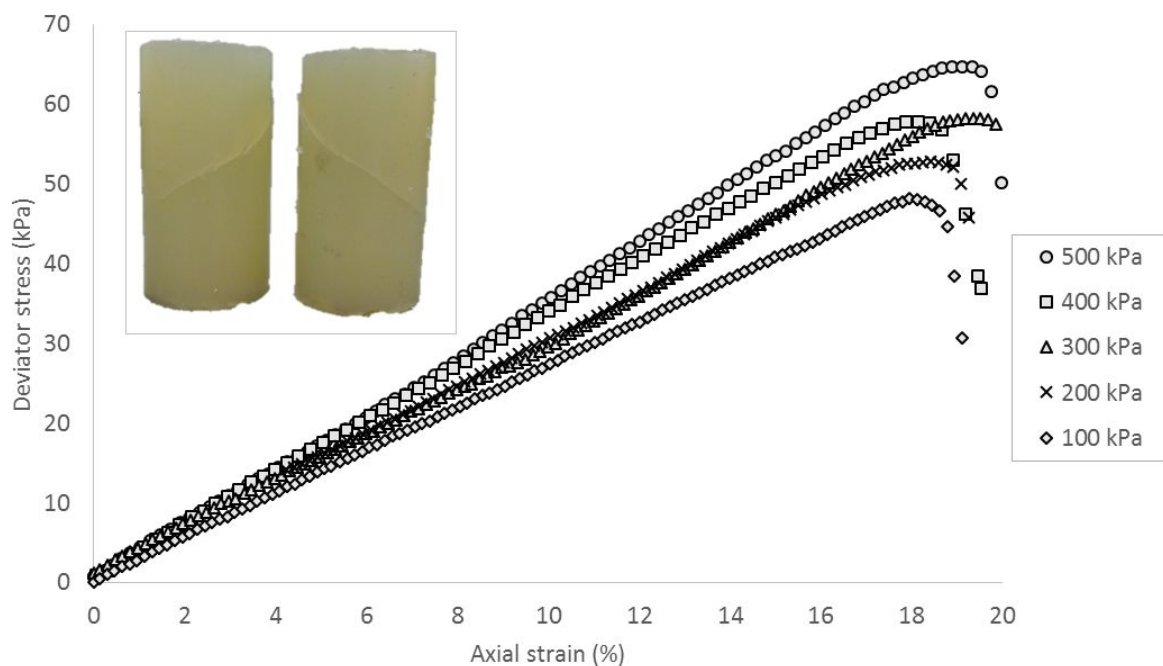


251

252 Fig. 3 shows that the maximum deviator stress increases with confining pressure (35.5%
 253 between the samples tested at 100kPa and 500kPa). The elastic modulus also increases with confining
 254 pressure (31.7% higher for the sample tested at 500kPa in comparison to the sample tested at
 255 100kPa). The results for undrained shear strength, maximum strain and elastic modulus for each of
 256 the specimens are summarised in Table 2. An average of these values gives a shear strength of 27 kPa,
 257 a maximum strain of 18% and a modulus of elasticity of 309 kPa for Agarose LM gel. A plot of the data
 258 in the form of Mohr's circles is also shown in Fig. 4.

259

260 Fig. 4. Unconsolidated-undrained triaxial test results in the form of Mohr's circles.

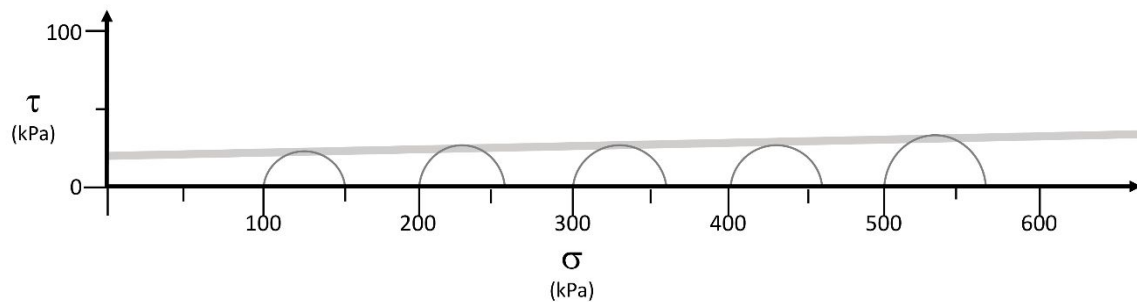

261

262 From Fig. 4 it can be seen that a tangent to the Mohr's circles is not perfectly horizontal, also
 263 demonstrating the increase in undrained shear strength shown in Table 2. As the samples are fully
 264 saturated (see 'Saturation of samples'), a possible explanation of the increase in undrained shear
 265 strength with confining pressure is a small leak in the triaxial cell causing minor consolidation. If this
 266 is the case, without the leak it would be expected that the shear strength would not increase and
 267 would be of a comparable magnitude to the lower values obtained.

268 Agarose LM gel samples were also loaded to different axial strains (2%, 4%, 6%, 8% and 10%)
 269 under a confining pressure of 500kPa and immediately unloaded, as can be seen from Fig. 5.


270

271

272

273

274 Fig. 5. Loading and unloading behaviour at different strain levels.

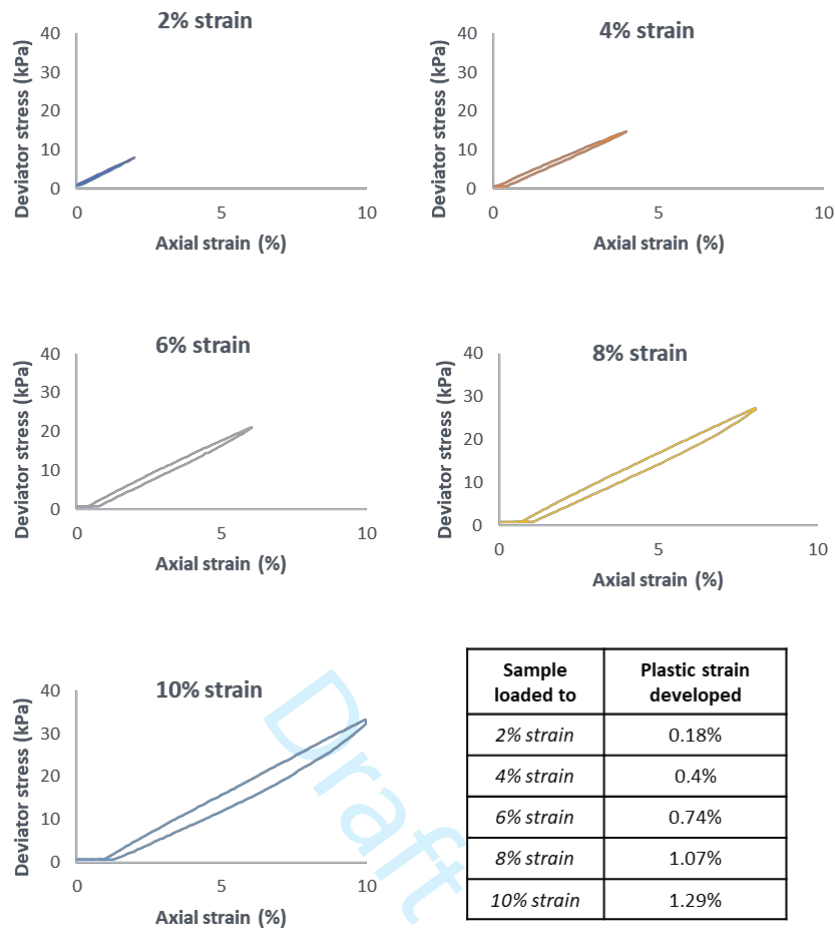

275

276 The residual/plastic axial strains developed after unloading are also summarised in Fig. 5.

277 These results show that Agarose LM gel presents short term mainly elastic behaviour although some

278 plastic strains do develop. Greater residual strains also develop at higher strain levels.

279

280 ***Anisotropic consolidation behaviour***

281 For the samples tested in the oedometer cell (one-dimensional consolidation), the rate of

282 change of axial strain in the samples decreased for every stage as consolidation occurred, allowing


283 calculation of the coefficient of consolidation. Fig. 6 shows all the stages of anisotropic consolidation

284 at 3 kPa, 6 kPa, 12 kPa, 25 kPa and 50 kPa, including both the loading and unloading stages.

285

286

287 Fig. 6. Anisotropic consolidation behaviour at different stress levels.

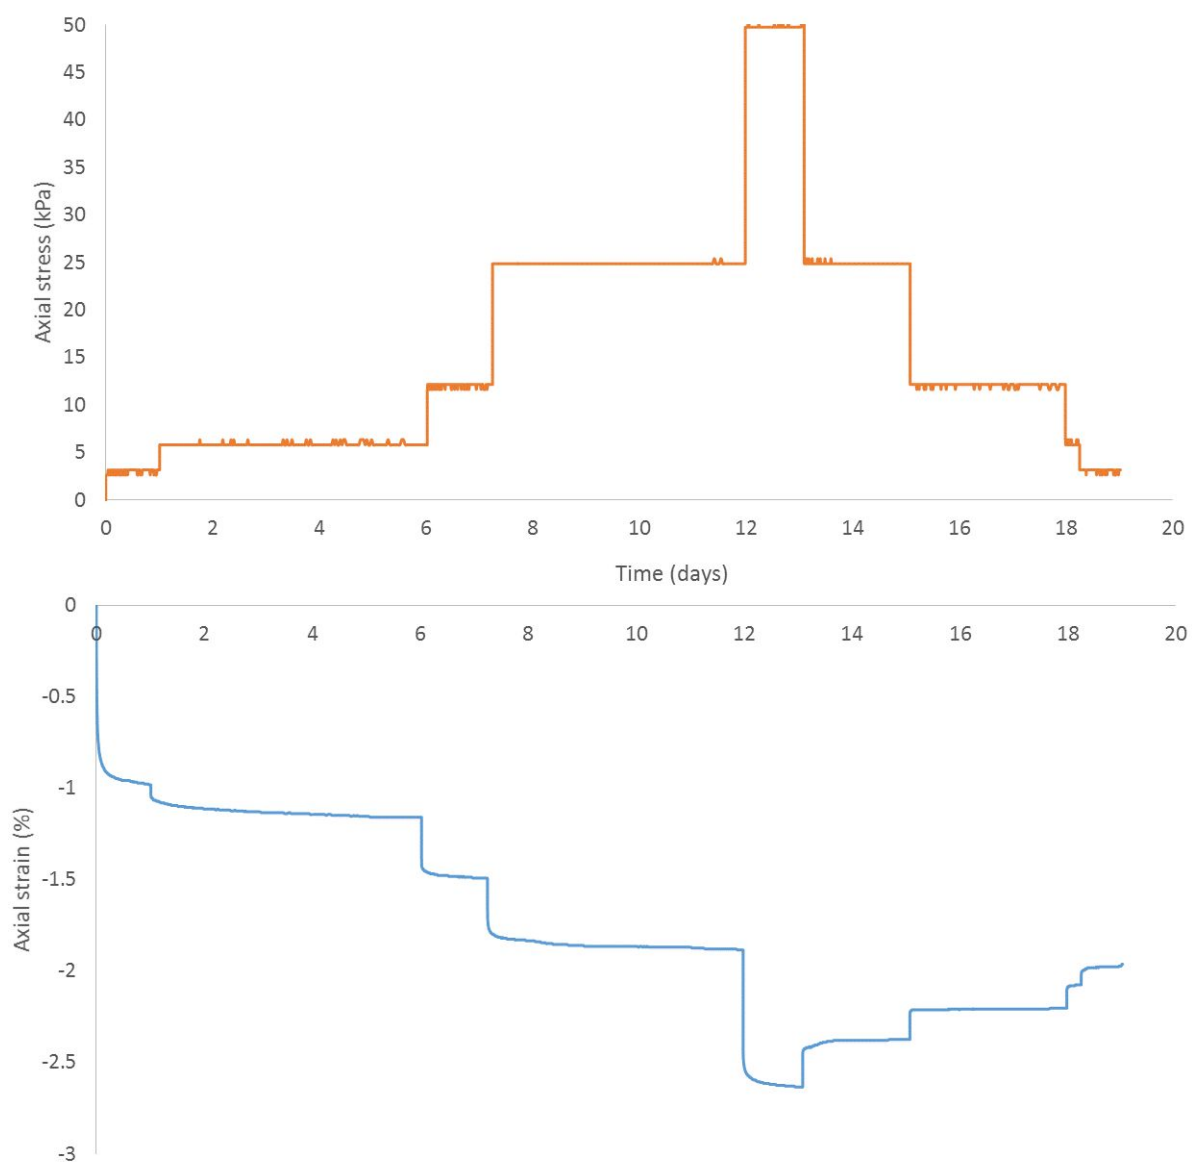

288


289 Taylor's method (British Standards Institution 1990c) for one-dimensional consolidation was
 290 used to calculate the coefficient of consolidation, c_v , for each loading stage. This method is based on
 291 the approximation that the relationship between axial displacement and time is parabolic for degree
 292 of consolidation $< 60\%$, therefore the relationship between the axial displacement and the square root
 293 of time is linear. Secondary consolidation is also assumed to be negligible for degree of consolidation
 294 $< 90\%$. Thus, c_v was calculated using t_{90} , according to the following expression (British Standards
 295 Institution 1990c):

$$(7) \quad c_v = \frac{0.446 * \bar{H}^2}{t_{90}}$$

where \bar{H} is the average height of the specimen between the start and the end of the consolidation stage and t_{90} is the time for 90% of consolidation. Fig. 7 shows the steps used to derive the value of t_{90} for the first stage at 3kPa. The values of c_v for every stage are given in Table 3 and range between 0.89-3.87 m²/year.

301

302 Fig. 7. Derivation of t_{90} .

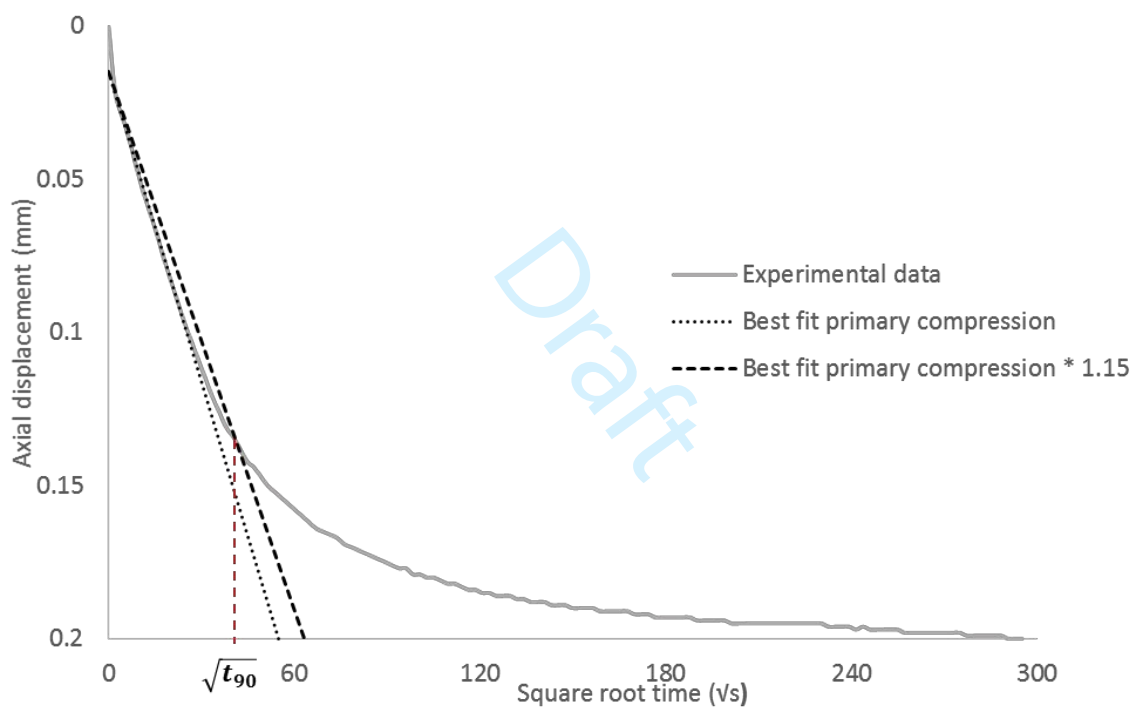

303

304

305 Additionally, the coefficient of volume compressibility, m_v was calculated according to the
 306 following expression (British Standards Institution 1990c):

$$(8) \quad m_v = \left(\frac{H_2 - H_1}{H_1} \right) \left(\frac{1000}{p_2 - p_1} \right)$$

308 where H_2 and H_1 are the height of the specimen at the end and start of the load increment, and p_2
 309 and p_1 are the pressures applied to the specimen for the previous and the considered loading stage,


310 respectively. The results for each consolidation stage are show in Table 4 and range between 0.3 and
 311 $3.26 \text{ m}^2/\text{MN}$.

312

313 ***Effect of consolidation on microstructure***

314 5 mm^3 cubes were extracted from one of the samples isotropically consolidated for 21 days
 315 at 100kPa and were prepared for SEM inspection as described in ‘Scanning Electron Microscope
 316 imaging’. Fig. 8 shows the microstructure of an unconsolidated sample and a sample consolidated for
 317 21 days. The structure is denser and the sizes of the pores are smaller for the consolidated sample,
 318 due to the drainage of water during consolidation. The pore size was measured as described in ‘Effect
 319 of concentration on microstructure’ and decreases from $0.3 \mu\text{m} \pm 0.09 \mu\text{m}$ when unconsolidated to
 320 $0.07\mu\text{m} \pm 0.016 \mu\text{m}$ after 21 days consolidation. This reduction in pore size is expected to result in a
 321 consequent decrease in permeability.

322 Fig. 8. Microstructure of consolidated (right) and unconsolidated (left) Agarose LM gel.

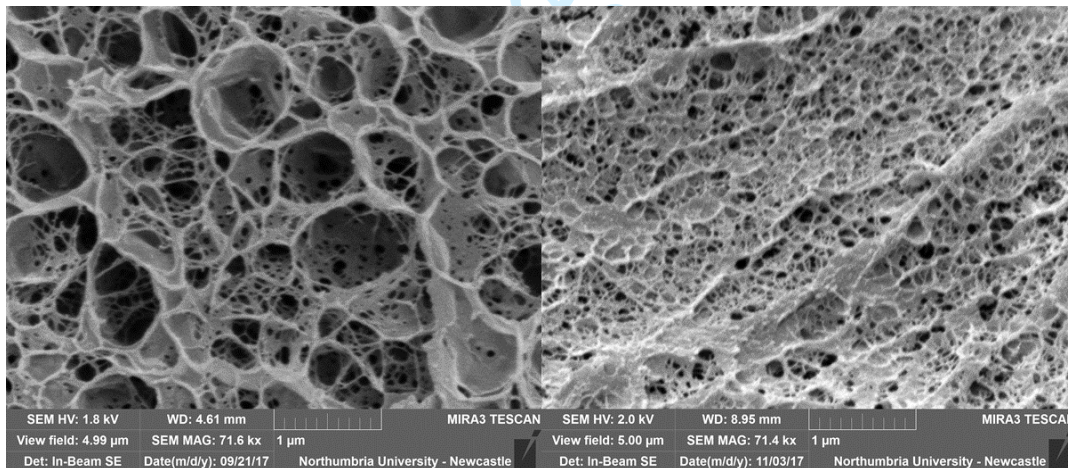

323

324

325 ***Permeability***

326 To estimate the vertical permeability, k_v the following expression derived from Darcy's law
 327 was used:

$$328 \quad (9) \quad k_v = \frac{1.63 * q * L * 10^{-4}}{A * (p_1 - p_2)}$$

329 where q is the mean rate of flow through the bottom of the specimen, L is the length of the specimen
330 prior to testing, A is the area of the specimen prior to testing and $p_1 - p_2$ is the pressure difference,
331 or consolidation pressure in this case. Thus, the vertical permeability k_v for 6% m/v Agarose LM gel
332 ranges between 3.4×10^{-11} and 8.8×10^{-11} m/s depending on the effective stress applied, as can
333 be seen from Table 5.

334 It should be noted that these results do not express directly measured values of the vertical
335 permeability, but an estimation made from the amount of fluid drained from the samples. However,
336 they provide a good indication of the permeability and allow a comparison with soils.

337

338

339 **Discussion: comparison to saturated cohesive soils**


340 Agarose LM gel has a fibrous microstructure that, although it is not granular, has a porous
341 structure similar to fine-grained soils. An experimental investigation was performed in order to
342 analyse the mechanical and physical properties of 6% m/v Agarose LM gel and Table 6 summarises the
343 results and provides a comparison to saturated cohesive soils for each of the properties. It should be
344 noted that while the type of behaviour is expected to be similar for other concentrations of agarose,
345 the magnitude of properties may be different.

346 It can be seen from Table 6 that there are a number of similarities between Agarose LM gel
347 and clays and peats, particularly the pore size, coefficient of consolidation and permeability values (as
348 shown more clearly in Fig. 9). The permeability of Agarose LM is expected to be higher in specimens
349 produced with lower concentrations of agarose (Narayanan et al. 2006, Pernodet et al. 1997), placing
350 it towards the higher end of the range of clay permeability (Fig. 9). The undrained shear strength and
351 undrained behaviour is also comparable to clays and can be analysed in similar way, as shown in Fig.
352 4. Additionally, SEM shows that a more densely packed structure is formed during consolidation,
353 suggesting that shear strength and stiffness of agarose gels will increase, which is similar to the
354 behaviour of most soils. The consolidation behaviour of Agarose LM shows a large proportion of

355 secondary compression however this is comparable to the behaviour of normally consolidated clays
 356 (Knappett and Craig, 2012).

357

358 Fig. 9. Comparison of permeability Agarose LM gel and soils, adapted from Carter and Bentley (1990).

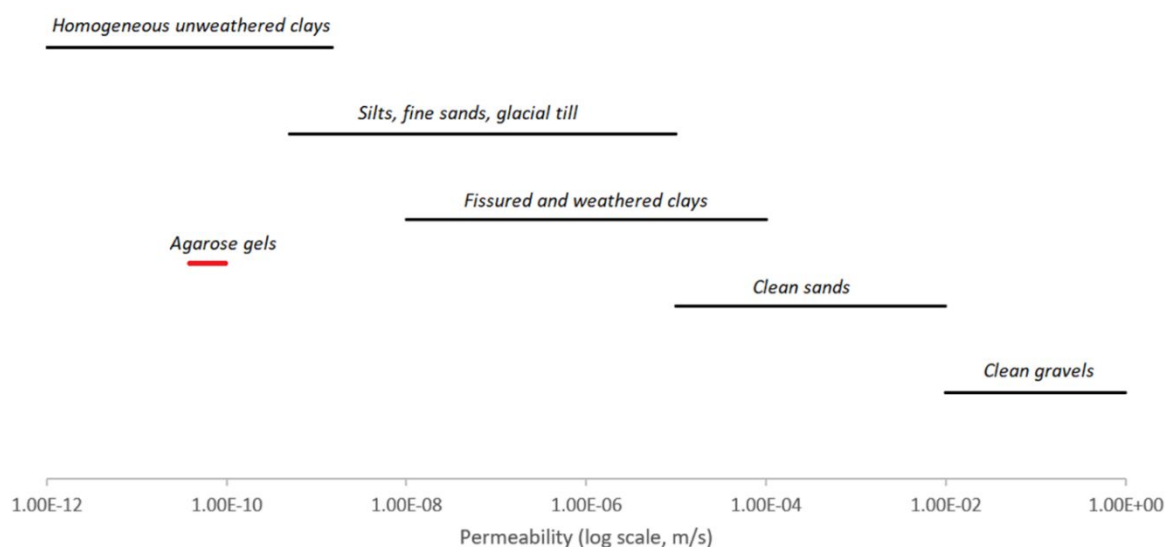

359


360 However, there are also significant differences between the properties of Agarose LM gel and
 361 soils. Agarose LM gel has a higher water content than any soil and consequently a much larger
 362 coefficient of volume compressibility than most soils. Only sensitive or highly organic clays and peats
 363 exhibit similar values (Carter and Bentley 1990). This high compressibility will result in much higher
 364 settlements when loaded, compared to soils.

365 The stress-strain behaviour of Agarose LM is also quite different to that of soil, as shown in
 366 Fig. 3 and in Fig. 10, compared to a kaolinite clay. The relationship is linear until failure (about 18-19%
 367 axial strain) for Agarose LM gel, in contrast to the behaviour of the kaolinite clay which is only linear
 368 at small-strains. For this region of linear stress-strain behaviour, the elastic modulus of very soft clays
 369 ranges between 2 and 15 MPa (Bowles 1996) These values are significantly higher than those of
 370 Agarose LM gel (approximately 0.3 MPa) but the gel is elastic over a much higher range of strains and
 371 shows significant recovery on unloading (Fig. 5). The implications of this are that Agarose LM gel may
 372 not be suitable as a soil analogue for an application where settlements must be reproduced. Agarose

373 LM gel will experience higher short-term settlements and less plastic deformation than a fine-grained
 374 soil.

375

376 Fig. 10. Comparison of stress-strain relationship of Agarose LM gel and kaolinite clay.

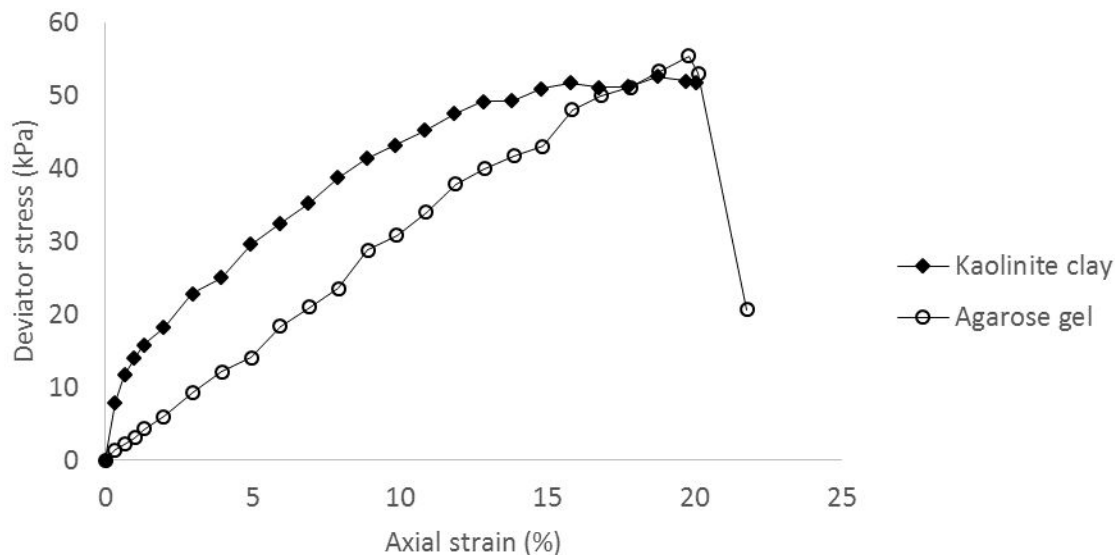

377

378

379

380 Conclusions

381 A programme of geotechnical tests and SEM was performed in order to determine the physical
 382 and mechanical properties of Agarose LM gel relevant to soil behaviour. A single concentration of
 383 agarose (6%*m/v*) was used for all mechanical tests. It should be noted that other types of agarose, or
 384 other concentrations may behave differently.

385 It is found that although the gel has a fibrous rather than granular structure, it has similar
 386 properties to some saturated cohesive soils such as soft clays or peats, including pore size, undrained
 387 strength, permeability and coefficient of consolidation. The comparable pore size to these types of
 388 soil means that bacteria are likely to grow and migrate in a similar way in both materials, making 6%
 389 Agarose LM gel a reasonable analogue if these aspects are of interest. Similarly, the comparable
 390 permeability to saturated cohesive soils means that the gel is a suitable analogue for developing bio-

391 mediated methods of contaminant removal, or for passive soil cementation methods which depend
392 on the flow of water through soils. Agarose LM gel is also currently being used as a soil analogue for
393 the development of a pressure-sensitive biological cementation method, as described by Dade-
394 Robertson *et al* (2018). This requires similar long-term behaviour of a saturated soil under load, so the
395 consolidation behaviour of Agarose LM gel makes it an ideal analogue in this case.

396 However, Agarose LM gel displays a much higher compressibility than soils and also behaves
397 mainly elastically, with very little permanent strains developing when unloaded. This means that
398 Agarose LM gel may not be a suitable soil analogue for applications where amount of settlement,
399 especially short-term settlement is important.

400 Agarose LM gel provides excellent conditions for growing and monitoring bacteria with a high
401 degree of chemical and physical control and many of the physical and mechanical properties of
402 cohesive soil are reproduced. Therefore Agarose LM gels can be an attractive option as a soil analogue
403 for researchers working in a laboratory environment on prototype advanced bio-mediated ground
404 improvement methods for these types of soils, for example contamination remediation and passive
405 or pressure responsive bio-cementation. Further investigation will be required to determine the
406 effects of different solvents on the mechanical properties of the gel, as well as different concentrations
407 and types of agarose. The range of properties available by changing these parameters may widen the
408 potential uses of agarose gel as a soil analogue.

409

410

411 **Acknowledgements**

412 This work was supported by the UK Engineering and Physical Sciences Research Council, grant
413 numbers EP/N005791/1, EP/R003629/1 and EP/R003777/1.

References

- Bowles, J.E. 1996. *Foundation Analysis and Design*. 5th ed. McGraw-Hill, New York.
- BSI (British Standards Institution). 1990a. *Methods of test for soils for civil engineering purposes - Part 2: Classification tests*, BS 1377-2:1990. London.
- BSI (British Standards Institution). 1990b. *Methods of test for soils for civil engineering purposes - Part 5: Compressibility, permeability and durability tests*, BS 1377-5:1990. London.
- BSI (British Standards Institution). 1990c. *Methods of test for soils for civil engineering purposes - Part 6: Consolidation and permeability tests in hydraulic cells and with pore pressure measurement*, BS 1377-6:1990. London.
- BSI (British Standards Institution). 1990d. *Methods of test for soils for civil engineering purposes - Part 7: Shear strength tests (total stress)*, BS 1377-7:1990. London.
- Carter, H. and Bentley, S.P. 1990. *Correlations of soil properties*. Pentech Press, London.
- Chu, J., Varaksin, S., Klotz, U. and Mengé, P. 2009. Construction processes. *In Proceedings of the 17th International Conference on Soil Mechanics and Geotechnical Engineering: The Academia and Practice of Geotechnical Engineering*, Alexandria, Egypt. pp. 3006-3135.
- Dade-Robertson, M., Mitrani, H., Rodriguez-Corral, J., Zhang, M., Hernan, L., Guyet, A. and Wipat, A. 2018. Design and modelling of an engineered bacteria-based, pressure sensitive soil. *Bioinspiration & Biomimetics*, **13**(4). doi: 10.1088/1748-3190/aabe15
- de Gennes, P.G. 1979. *Scaling Concepts in Polymer Physics*. Cornell University Press, Ithaca, New York.
- DeJong, J.T., Martinez, B.C., Mortensen, B.M., Nelson, D.C., Waller, J.T., Weil, M.H., Ginn, T.R., Weathers, T., Barkouki, T., Fujita, Y., Redden, G., Hunt, C., Major, D. and Tanyu, B. 2009. Upscaling of bio-mediated soil improvement. *In Proceedings of the 17th International Conference on Soil Mechanics and Geotechnical Engineering: The Academia and Practice of Geotechnical Engineering*, Alexandria, Egypt. pp. 2300–2303. doi:10.3233/978-1-60750-031-5-2300.
- DeJong, J.T., Mortensen, B.M., Martinez, B.C. and Nelson, D.C. 2010. Bio-mediated soil

- improvement. *Ecological Engineering*, **36**: 197–210. doi:10.1016/j.ecoleng.2008.12.029.
- DeJong, J.T., Soga, K., Kavazanjian, E., Burns, S., van Paasen, L., Al Qabany, A., Aydilek, A., Bang, S.S., Burbank, M., Caslake, L.F., Chen, C.Y., Cheng, X., Chu, J., Ciurli, S., Esnault-Filet, A., Fauriel, S., Hamdan, N., Hata, T., Inagaki, Y., Jefferis, S., Kuo, M., Laloui, L., Larrahondo, J., Manning, D.A.C., Martinez, B., Montoya, B.M., Nelson, D.C., Palomino, A., Renforth, P., Santamarina, J.C., Seagren, E.A., Tanyu, B., Tsesarsky, M. and Weaver, T. 2013. Biogeochemical processes and geotechnical applications: progress, opportunities and challenges. *Géotechnique*, **63**(4): 287–301. doi:10.1680/geot.SIP13.P.017.
- Endy, D. 2005. Foundations for engineering biology. *Nature*, **438**: 449 - 453. doi:10.1038/nature04342.
- Horemans, B., Breugelmans, P., Saeys, W. and Springael, D. 2017. Soil-Bacterium Compatibility Model as a Decision-Making Tool for Soil Bioremediation. *Environmental Science and Technology*, **51**(3): 1605 -1615. doi:10.1021/acs.est.6b04956.
- Ionov, L. 2014. Hydrogel-based actuators: possibilities and limitations. *Materials Today*, **17**(10): 494-503. doi: 10.1016/j.mattod.2014.07.002
- Ivanov, V. and Chu, J. 2008. Applications of microorganisms to geotechnical engineering for bioclogging and biocementation of soil in situ. *Reviews in Environmental Science and Biotechnology*, **7**(2): 139–153. doi:10.1007/s11157-007-9126-3.
- Johnson, E.M., Berk, D.A., Jain, R.K. and Deen, W.M. 1995. Diffusion and partitioning of proteins in charged agarose gels. *Biophysical Journal*, **68**(4): 1561–1568. doi:10.1016/S0006-3495(95)80328-0.
- Knappett, J. and Craig, R.F. 2012. *Craig's Soil Mechanics*. 8th ed. Spon, London.
- Martinez, B.C., DeJong, J.T. and Ginn, T.R. 2014. Bio-geochemical reactive transport modeling of microbial induced calcite precipitation to predict the treatment of sand in one-dimensional flow. *Computers and Geotechnics*, **58**: 1–13. doi:10.1016/j.compgeo.2014.01.013.
- Laurent, T.C. 1967. Determination of the structure of agarose gels by gel chromatography. *Biochimica et Biophysica Acta – General Subjects*, **136**(2): 199–205. doi: 10.1016/0304-

4165(67)90064-5

Narayanan, J., Xiong, J.-Y. and Liu, X.-Y. 2006. Determination of agarose gel pore size: Absorbance measurements vis a vis other techniques. *Journal of Physics: Conference Series*, **28**.

doi:10.1088/1742-6596/28/1/017.

Ogston, A.G. 1958. The spaces in a uniform random suspension of fibres. *Transactions of the Faraday Society*, **54**: 1754–1757. doi: 10.1039/TF9585401754

Ogston, A.G., Preston, B.N., Wells, J.D. and Snowden, J.M. 1973. On the transport of compact particles through solutions of chain-polymers. *Proceedings of the Royal Society A*, **333**(1594): 297–316. doi:10.1098/rspa.1973.0064.

Pernodet, N., Maaloum, M., and Tinland, B. 1997. Pore size of agarose gels by atomic force microscopy. *Electrophoresis*, **18**(1): 55–58. doi:10.1002/elps.1150180111.

Pluen, A., Netti, P.A., Jain, R.K. and Berk, D.A. 1999. Diffusion of macromolecules in agarose gels: comparison of linear and globular configurations. *Biophysical Journal*, **77**(1): 542–552.

doi:10.1016/S0006-3495(99)76911-0.

Powrie, W. 2014. *Soil Mechanics: Concepts and Applications*, 3rd ed. CRC Press/Taylor & Francis, Boca Raton, Florida, USA.

Robards, A.W. 1991. Rapid-freezing methods and their applications. *In* *Electron microscopy of plant cells*. Edited by J.L. Hall and C. Hawes. Elsevier. pp. 257–312. doi: 10.1016/B978-0-12-318880-9.X5001-7

Skempton, A.W. 1954. The pore-pressure coefficient A and B. *Géotechnique*, **4**(4): 143–147.

doi:10.1680/geot.1954.4.4.143

Smith, I.K. 2014. *Smith's Elements of Soil Mechanics*, 9th ed. Wiley-Blackwell, West Sussex, U.K.

Stabnikov, V., Ivanov, V. and Chu, J. 2015. Construction Biotechnology: a new area of biotechnological research and applications. *World Journal of Microbiology and Biotechnology*, **31**(9): 1303–1314. doi:10.1007/s11274-015-1881-7.

Stellwagen, J. and Stellwagen, N.C. 1995. Internal Structure of the Agarose Gel Matrix. *Journal of*

Physical Chemistry, **99**(12): 4247–4251. doi:10.1021/j100012a054.

Varaprasad, K., Raghavendra, G.M., Jayaramudu, T., Yallapu, M.M. and Sadiku, R. 2017. A mini review on hydrogels classification and recent developments in miscellaneous applications. *Materials Science and Engineering: C*, **79**: 958-971. doi: 10.1016/j.msec.2017.05.096

Whiffin, V.S., van Paassen, L.A. and Harkes, M.P. 2007. Microbial Carbonate Precipitation as a Soil Improvement Technique. *Geomicrobiology Journal*, **24**(5): 417-423.

doi:10.1080/01490450701436505.

White, C., Shaman, A.K. and Gadd, G.M. 1998. An integrated microbial process for the bioremediation of soil contaminated with toxic metals. *Nature Biotechnology*, **16**: 572-575.

doi.org/10.1038/nbt0698-572.

Zhang, Y.S. and Khademhosseini, A. 2017. Advances in engineering hydrogels. *Science*, **356**(6337).

doi: 10.1126/science.aaf3627

Draft

Tables

Table 1. Porosity, void ratio and moisture content.

	Porosity, n	Void ratio, e	Moisture Content, w
Theoretical	0.94	16.1	16.7
Average Experimental	0.96	26.0	15.8

Draft

Table 2. Shear strength, maximum axial strain and elastic modulus.

Confining pressure (kPa)	Undrained Shear strength, c_u (kPa)	Maximum strain (%)	Elastic modulus (kPa)
100	23	18	268
200	25	18	297
300	28	19	299
400	28	18	328
500	31	19	353

Draft

Table 3. Coefficient of consolidation, c_v for each consolidation stage.

Axial Stress (kPa)	Coefficient of Consolidation, c_v (m ² /year)
3	3.13
6	0.89
12	1.16
25	1.56
50	3.87

Draft

Table 4. Coefficient of volume compressibility, m_v for each consolidation stage.

Axial Stress (kPa)	Coefficient of Volume Compressibility, m_v (m^2/MN)
3	3.26
6	0.59
12	0.56
25	0.3
50	0.3

Draft

Table 5. Derivation and values of vertical permeability, k_v .

Pressure gradient (kPa)	Flow rate (mL/min)	Specimen length (mm)	Area (mm ²)	Vertical permeability, k_v (m/s)
25	0.000088	74.35	1046.35	4.1×10^{-11}
50	0.00038	75.40	1046.35	8.8×10^{-11}
100	0.00041	74.96	1081.03	4.6×10^{-11}
150	0.00045	75.60	1086.86	3.4×10^{-11}

Draft

Table 6. Comparison of mechanical properties Agarose LM gel and soils.

Properties	Values	Comparable to
Water content (%)	1583	-
Porosity	0.96	-
Void ratio	26.0	-
Pore size (μm)	0.21 – 0.39	Homogeneous clay soils (0.2-1) ¹
Undrained shear strength, c_u (kPa)	27	Soft clays (20 - 40kN/m ²) ² . Kaolinite clay ($c_u = 25\text{-}27\text{kPa}$) ³
Maximum axial strain (%)	18	Kaolinite clay (20%) ³
Elastic modulus (kPa)	309	-
Coefficient of consolidation (m ² /year)	0.89 - 3.87	Organic silts (0.6 - 3m ² /year), glacial clays (2.0 – 2.7m ² /year) and Chicago silty clays (2.7m ² /year) ²
Coefficient of volume compressibility (m ² /MN)	0.3 - 3.27	Sensitive clays (0.3 – 1.5m ² /MN) and highly organic soils (1.5m ² /MN) ²
Vertical permeability (m/s)	3.4×10^{-11} – 8.8×10^{-11}	Homogeneous clay soils (see Fig. 9)

¹(Powrie 2014)

²(Carter and Bentley 1990)

³Experimental testing

Draft

Figure Captions

Fig. 1. SEM images of microstructure at mass concentrations of 2% (left), 4% (middle) and 6% (right).

Fig. 2. Pore size as a function of agarose concentration.

Fig. 3. Stress-strain relationship at different confining pressures, with inset of samples showing failure surface.

Fig. 4. Unconsolidated-undrained triaxial test results in the form of Mohr's circles.

Fig. 5. Loading and unloading behaviour at different strain levels.

Fig. 6. Anisotropic consolidation behaviour at different stress levels.

Fig. 7. Derivation of t_{90} .

Fig. 8. Microstructure of consolidated (right) and unconsolidated (left) Agarose LM gel.

Fig. 9. Comparison of permeability Agarose LM gel and soils, adapted from Carter and Bentley (1990).

Fig. 10. Comparison of stress-strain relationship of Agarose LM gel and kaolinite clay.