

## Journal Pre-proofs

Wear resistant CoCrFeMnNi<sub>0.8</sub>V High Entropy Alloy with Multi Length-Scale Hierarchical Microstructure

S. González, A.K. Sfikas, Spyros Kamnis, Carlos Garay, A. Hurtado-Macias, R. Martínez-Sánchez

PII: S0167-577X(22)01859-6  
DOI: <https://doi.org/10.1016/j.matlet.2022.133504>  
Reference: MLBLUE 133504

To appear in: *Materials Letters*

Received Date: 28 October 2022  
Revised Date: 8 November 2022  
Accepted Date: 9 November 2022

Please cite this article as: S. González, A.K. Sfikas, S. Kamnis, C. Garay, A. Hurtado-Macias, R. Martínez-Sánchez, Wear resistant CoCrFeMnNi<sub>0.8</sub>V High Entropy Alloy with Multi Length-Scale Hierarchical Microstructure, *Materials Letters* (2022), doi: <https://doi.org/10.1016/j.matlet.2022.133504>

This is a PDF file of an article that has undergone enhancements after acceptance, such as the addition of a cover page and metadata, and formatting for readability, but it is not yet the definitive version of record. This version will undergo additional copyediting, typesetting and review before it is published in its final form, but we are providing this version to give early visibility of the article. Please note that, during the production process, errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

© 2022 The Author(s). Published by Elsevier B.V.



## Wear resistant CoCrFeMnNi<sub>0.8</sub>V High Entropy Alloy with Multi Length-Scale Hierarchical Microstructure

S. González<sup>1,\*</sup>, A. K. Sfikas<sup>1</sup>, Spyros Kamnis<sup>2</sup>, Carlos Garay<sup>3</sup>, A. Hurtado-Macias<sup>3</sup>, R. Martínez-Sánchez<sup>3</sup>

<sup>1</sup>Faculty of Engineering and Environment, Northumbria University, Newcastle upon Tyne, NE1 8ST, UK

<sup>2</sup>Castolin Eutectic-Monitor Coatings Ltd, Newcastle upon Tyne, NE29 8SE, UK

<sup>3</sup>Centro de Investigación en Materiales Avanzados (CIMAV), Laboratorio Nacional de Nanotecnología, Miguel de Cervantes 120, 31136 Chihuahua, Chih., México.

\* Corresponding author at: Faculty of Engineering and Environment, Northumbria University, Newcastle upon Tyne, NE1 8ST, UK. *E-mail address:* Sergio.sanchez@northumbria.ac.uk (S. González).

### Abstract

This work shows a CoCrFeMnNi<sub>0.8</sub>V high entropy alloy (HEA) with multiple length-scale hierarchical microstructure, obtained upon cooling at ~ 62.5 K/s, consisting of a dominant globular sigma phase, FCC matrix and V-rich particles. The novel microstructure, never reported before for the CoCrFeMnNiV system, results in about a fourfold and sixfold increase of hardness and wear resistance, respectively, compared to that of CoCrFeMnNi alloy.

Keywords: Metal and alloys; Indentation and hardness; Wear and tribology; Solidification

### 1. Introduction

The most well known among all FCC-type high entropy alloys (HEAs) is the CrMnFeCoNi (Cantor alloy) [1,2]. The addition of Cr and Mn destabilise single phase solid solution and promotes the formation of  $\sigma$  phase while Ni is a strong FCC stabiliser and suppresses the formation of  $\sigma$  phase [3]. The effect of Ni on CoCrFeMnNi<sub>x</sub>V alloy is similar since it reduces the volumen fraction of  $\sigma$  phase and therefore decreases the microhardness from 12 GPa for CoCrFeMnV to 4.1 GPa for CoCrFeMnNi<sub>3</sub>V [4]. However, the microstructure of the novel composition CoCrFeMnNi<sub>0.8</sub>V produced upon casting at a cooling rate of ~ 62.5

K/s and its influence on the hardness and wear resistance have not been studied before.

## 2. Experimental procedure

The master alloys were fabricated from elements with purity higher than 99.9 at.%. Subsequently they were re-melted at least three times using a Zr-getter in a high purity argon atmosphere. Rod samples of 8 mm diameter were obtained by melting the master alloy into a water-cooled copper mould in an inert gas atmosphere. X-ray diffraction (XRD) was used to analyse the structure. A Scanning Electron Microscope (SEM) and Transmission Electron Microscope (TEM) with energy-dispersive X-ray (EDX) analysis were used to analyse the microstructures. Nanoindentation experiments were performed at room temperature in a UMIS equipment from Fischer-Cripps Laboratories, in the load control mode and using a Berkovich-type diamond tip. The surfaces were mirror-like polished prior to the tests. From the 9 nanoindentations performed and the high load applied (2 mN) we have sampled all the existing phases and obtained a statistical mean value. The nanoindentation equipment was used in scratch mode for the scratch tests of the mirror-like polished samples. The 50  $\mu\text{m}$  length scratches were performed at a load of 1.5 mN at a stage speed of 20  $\mu\text{m/s}$ .

## 3. Results and discussion

The cooling rate  $\dot{T}$  of the CoCrFeMnNi and CoCrFeMnNi<sub>0.8</sub>V suction cast alloys can be estimated from the relationship [5]:

$$\dot{T}\left(\frac{K}{s}\right) = \frac{10}{R^2}\left(\frac{1}{cm^2}\right) \quad (1)$$

where R (4 mm) is the sample radius; hence the cooling rate is  $\sim 62.5$  K/s for both compositions. [Figure 1](#) shows the X-ray diffractograms, backscattered SEM images and compositional mappings for of the alloys. For CoCrFeMnNi, the XRD peaks are associated to a single FCC phase while for CoCrFeMnNi<sub>0.8</sub>V the XRD peaks correspond to body centred tetragonal  $\sigma$  phase (most abundant) and FCC phase.

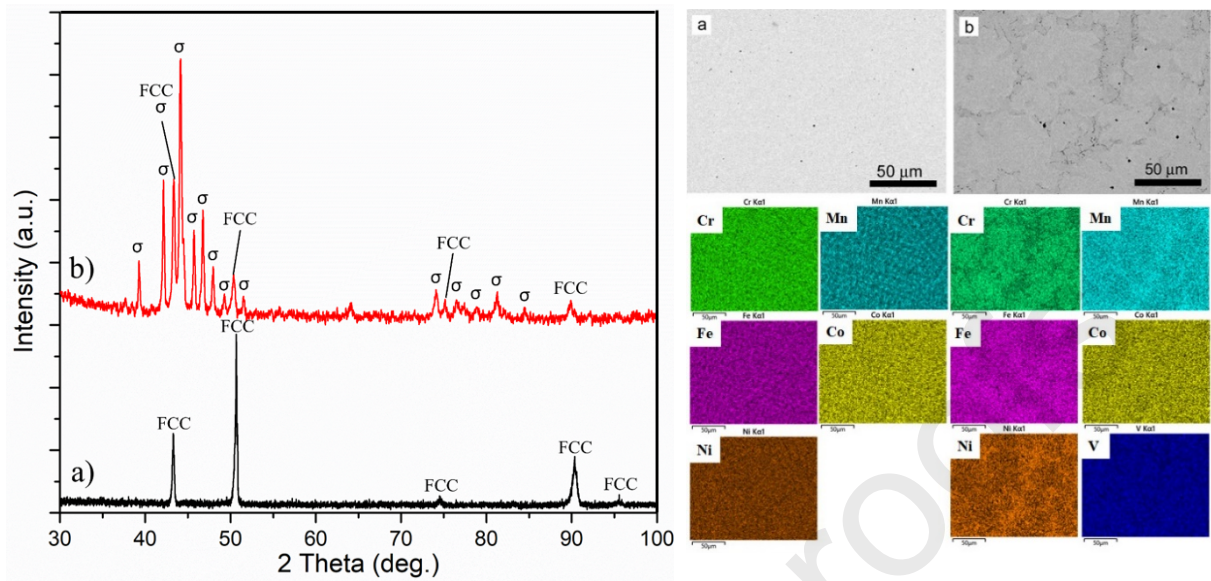


Fig. 1. X-ray diffractograms for a) CoCrFeMnNi and b) CoCrFeMnNi<sub>0.8</sub>V and backscattered SEM images with compositional mappings for: a) CoCrFeMnNi and b) CoCrFeMnNi<sub>0.8</sub>V.

For CoCrFeMnNi HEA (Fig. 1a), the microstructure is basically featureless. However, for CoCrFeMnNi<sub>0.8</sub>V (Fig. 1b) it consists of dendrites of clear tonality surrounded by a matrix containing tiny dark particles mostly decorating the borders of the dendrites, something intimately connected with the so-called complete and incomplete wetting of grain boundaries by the liquid or second solid phase [6, 7]. The presence of the tiny dark particles (lenticular precipitates) seem to precipitate with non-zero contact angle thus suggesting incomplete (partial) wetting. The compositional mappings suggest the CoCrFeMnNi alloy is chemically homogeneous. However, for CoCrFeMnNi<sub>0.8</sub>V, a Cr-rich globular phase surrounded by a Ni-rich matrix is detected, while the distribution of Mn, V, Fe and Co is constant throughout both regions. The Cr-rich phase corresponds to the  $\sigma$  phase, while the Ni-rich phase is associated to the FCC solid solution. The TEM image for CoCrFeMnNi (Fig. 2a) and corresponding compositional mapping (Fig. 2b) shows an homogeneous distribution of the elements throughout the sample, without any sign of segregation to the grain boundaries, thus confirming the previous results (Fig. 1). For the CoCrFeMnNi<sub>0.8</sub>V HEA, the backscattered SEM image of Fig. 2c shows dark particles of about 1  $\mu\text{m}$  size that according to the TEM mapping (see inset of Fig. 2c), they are very rich in V

element and contains cobalt. From linear intercept analysis, the volume fraction of the different phases are:  $\sigma$  phase (~82 vol. %), FCC phase (~13 vol. %) and V-rich particles (<5 vol. %). These particles are finely and homogeneously distributed across the sample and therefore are not the result of unmelted element. To the author's knowledge, this is the first time that such a hierarchical microstructure containing V-rich particles is detected, not present even for similar compositions such as CoCrFeMnNiV HEA [4].

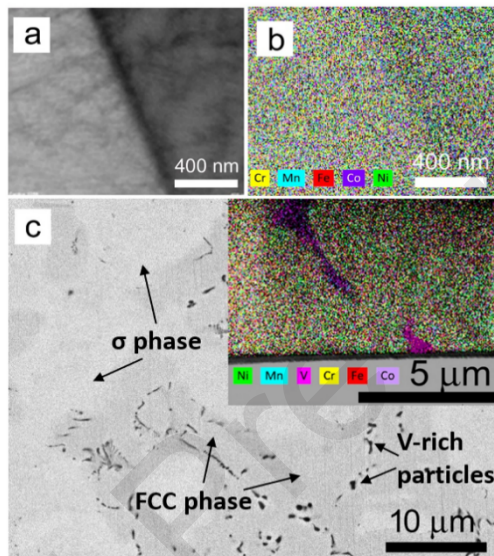


Fig. 2. a) TEM image for CoCrFeMnNi and b) corresponding elemental mapping. C) backscattered SEM image for CoCrFeMnNi<sub>0.8</sub>V and inset showing elemental TEM mapping of the V-rich particles.

The formation of these V-rich particles seems to be mostly promoted by the relatively low Ni content and therefore the higher probability of the V atoms to be surrounded by the Co, Cr, Fe and Mn atoms while the small particle size and heterogeneous distribution would be favoured by the high cooling rate. From a thermodynamic point of view, the V-Co pairs are more likely to be formed taking into consideration the heats of mixing (V-Co: -14 KJ/mol, V-Ni: -18 KJ/mol, V-Cr: -2 KJ/mol; V-Fe: -7 KJ/mol and V-Mn: -1 KJ/mol [8]). Figure 3 shows the representative load-displacement (P-h) curves when testing (a) CoCrFeMnNi, (b) CoCrFeMnNi<sub>0.8</sub>V and also each individual phase: (b1)  $\sigma$  phase and (b2) matrix (FCC+V-rich particles). The maximum indentation depth, also called displacement depth,  $h_{max}$ , decreases from 129.9  $\mu\text{m}$  for CoCrFeMnNi to 70.8  $\mu\text{m}$



for CoCrFeMnNi<sub>0.8</sub>V, probably due to the large volume fraction of hard  $\sigma$  phase and V-rich particles. To better understand the contribution of the  $\sigma$  phase and matrix (FCC + V-rich particles) on the overall mechanical behaviour they have been indented individually (Fig. 3).

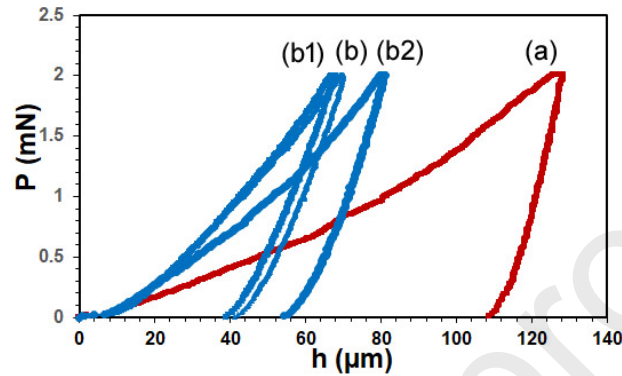


Fig. 3. Load-displacement (P-h) nanoindentation curves for (a) CoCrFeMnNi, (b) CoCrFeMnNi<sub>0.8</sub>V, (b1)  $\sigma$  phase and (b2) matrix.

The wear resistance can be estimated from the  $H/E_r$  ratio [9]. This parameter can therefore be used to estimate the wear resistance of each individual phase. For  $\sigma$  phase the  $H/E_r$  ratio is 0.057 while for the matrix (FCC + V-rich particles) it is 0.039, therefore most of the wear resistance contribution is attributed to the  $\sigma$  phase (~82 vol. %). The relatively small  $h_{max}$  value for the CoCrFeMnNi<sub>0.8</sub>V is consistent with the hardness since it is higher for CoCrFeMnNi<sub>0.8</sub>V, i.e., 13.09 GPa than for CoCrFeMnNi, i.e., 3.80 GPa. The  $H/E_r$  ratio is higher for CoCrFeMnNi<sub>0.8</sub>V (i.e., 0.049) than for CoCrFeMnNi (i.e., 0.018), a threefold wear resistance increase. The wear resistance has been also studied directly from nanoscratch tests on CoCrFeMnNi (Fig. 4a) and CoCrFeMnNi<sub>0.8</sub>V (Fig. 4b) by performing 50  $\mu$ m long nanoscratches, long enough to embrace all the phases.

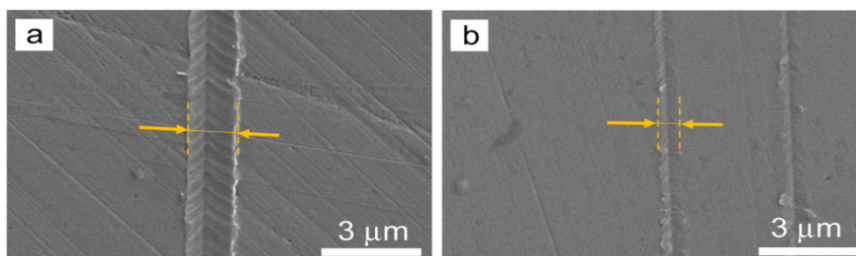


Fig. 4. SEM Images showing the scratches on the samples (a) for CoCrFeMnNi and (b) CoCrFeMnNi<sub>0.8</sub>V HEAs.

The scratch width for CoCrFeMnNi is 1.5  $\mu\text{m}$ , while for CoCrFeMnNi<sub>0.8</sub>V (see yellow arrows in Fig. 4a and 4b, respectively) it is only 0.6  $\mu\text{m}$ . A useful parameter to study the wear resistance of materials is the scratch hardness number, which is given by the following equation [10]:

$$H_s = q \frac{4 * P}{\pi * w^2}, \quad (2)$$

where P (N) the normal load, w' (m) the scratch width and H<sub>s</sub> (Pa) is the scratch hardness. For these alloys, the response can be approximated to a rigid plastic and therefore q = 2, which is also used in metallic composites [11]. From equation 1, the scratch hardness of CoCrFeMnNi equals 1.70 GPa while for CoCrFeMnNi<sub>0.8</sub>V it is 10.61 GPa, much higher than for Stellite® 6 (4.3 GPa) and for FeCoCrNiW<sub>0.3</sub> (1.25 GPa), FeCoCrNiW<sub>0.3</sub> + 5 a. % C (4.5 GPa) [12]. No cracks have been detected around the scratches and no pop-ins associated to the formation of cracks are detected (Fig. 3), thus suggesting the CoCrFeMnNi<sub>0.8</sub>V HEA is more ductile than other alloys such as metallic glass composites [13]. Another important parameter that can be obtained from the scratch tests are the pile-up height and total groove depth, which are indicative of how ductile or brittle a material is. The groove height for CoCrFeMnNi and CoCrFeMnNi<sub>0.8</sub>V are 134 and 26 nm, respectively, while the pile-up height is 32 nm and 21 nm respectively, which is consistent with the higher wear resistance of CoCrFeMnNi<sub>0.8</sub>V alloy.

This work demonstrates that the microstructure of the CoCrFeMnNiV alloy system is very sensitive to small changes in composition and cooling rate, which enables to easily tweak their performance for their practical application in industry. For example, the hardness of the novel CoCrFeMnNi<sub>0.8</sub>V is higher than for CoCrFeMnV, while the opposite should be expected [4]. This could be attributed to the hierarchical microstructure containing V-rich particles when cooling at ~ 62.5 K/s.

#### 4. Conclusions

The following conclusions can be drawn:

1. A novel CoCrFeMnNi<sub>0.8</sub>V high entropy alloy (HEA) with multi length-scale hierarchical microstructure consisting of sigma phase (~82 vol. %), FCC phase (~13 vol. %) and V-rich particles containing Co (<5 vol. %) is obtained directly upon suction casting at a cooling rate of ~ 62.5 K/s.
2. The hardness for CoCrFeMnNi<sub>0.8</sub>V, 13.09 GPa, is nearly 4 times higher than for CoCrFeMnNi while the scratch hardness number, a measure of the wear resistance, is 10.61 GPa, about 6 times higher than for CoCrFeMnNi.
3. The presence of V-rich particles is detected for the first time in the CoCrFeMnNiV alloy system.
4. This work demonstrates that combined small changes of composition and cooling rate can lead to a CoCrFeMnNi<sub>0.8</sub>V alloy of potential interest for durable components.

#### **Declaration of Competing Interest**

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

#### **Acknowledgements**

The authors would like to acknowledge the support from the UK Research & Innovation (UKRI-IUK) national funding agency. Project Grant: 53662 '*Design of High-Entropy Superalloys Using a Hybrid Experimental-Based Machine Learning Approach: Steel Sector Application*'. The authors are deeply grateful to Roberto P. Talamantes Soto for his valuable support with scratch tests.

#### **References**

- [1] B. Cantor, I.T.H. Chang, P. Knight, A.J.B. Vincent, Mater. Sci. Eng. A, 375-377 (2004) 213-218.
- [2] J.W. Yeh, S.K. Chen, S.J. Lin, J.Y. Gan, T.S. Chin, T.T. Shun, C.H. Tsau, S.Y. Chang, Adv. Eng. Mater. 6 (2004) 299-303.
- [3] K.A. Christofidou, T.P. McAuliffe, P.M. Mignanelli, H.J. Stone, N.G. Jones, J. Alloys Compd. 770 (2019) 285-293.



- [4] M.V. Karpets', O.M. Myslyvchenko, O.S. Makarenko, J. Superhard Mater. 37 (2015) 182–188.
- [5] X. Lin, W. Johnson, J. Appl. Phys. 78 (1995) 6514
- [6] B.B. Straumal, A. Korneva, A. Kuzmin, G.A. Lopez, E. Rabkin, A.B. Straumal, G. Gerstein, A.S. Gornakova, Metals 11 (2021) 1881.
- [7] B.B. Straumal, A. Korneva, G.A. Lopez, A. Kuzmin, E. Rabkin, G. Gerstein, A.B. Straumal, A.S. Gornakova, Materials 14 (2021) 7506.
- [8] F. R. Boer, D. G. Perrifor, Cohesion in Metals, Elsevier Science Publishers B.V., Netherlands, 1988.
- [9] A. Leyland, A. Matthews, Wear 246 (2000) 1–11.
- [10] M. Villapún, F. Esat, S. Bull, L.G. Dover, S. González, Materials 10 (2017) 506.
- [11] S.K. Sinha, S.U. Reddy, M. Gupta, Tribol. Int. 39 (2006) 184–189.
- [12] M.G. Poletti, G. Fiore, F. Gili, D. Mangherini, L. Battezzati, Mater. Design 115 (2017) 247–254.
- [13] V.M. Villapún, H. Zhang, C. Howden, L. Cheung Chow, F. Esat, P. Pérez, J. Sort, S. Bull, J. Stach, S. González, Materials & Design 115 (2017) 93-102.

**S. González:** Conceptualization, Writing- Original draft preparation, Supervision, Investigation. **A. K. Sfikas:** Writing- Original draft preparation, Investigation, **Spyros Kamnis:** Investigation, Funding acquisition. **Carlos Garay:** Investigation, Formal analysis. **A. Hurtado-Macias:** Roles/Writing - original draft, Investigation. **R. Martínez-Sánchez:** Investigation, Formal analysis

#### Declaration of interests

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

The authors declare the following financial interests/personal relationships which may be considered as potential competing interests:

Spyros Kamnis reports financial support was provided by UK Research and Innovation. NA reports a relationship with NA that includes: NA has patent NA pending to NA. No conflict of interests.

## Highlights

- V-rich particles are detected for the first time in the CoCrFeMnNiV alloy system.
- A novel microstructure for CoCrFeMnNi<sub>0.8</sub>V is achieved upon cooling at ~ 62.5 K/s.
- The hardness and wear resistance are higher than for CoCrFeMnNi alloy.